

THE USE OF LIMESTONE AGGREGATE IN CONCRETE

MUSFA BIN MOHAMAD

UNIVERSITI TEKNOLOGI MALAYSIA

UNIVERSITI TEKNOLOGI MALAYSIA

BORANG PENGESAHAN STATUS LAPORAN PROJEK SARJANAJUDUL: THE USE OF LIMESTONE AGGREGATE IN CONCRETE.SESI PENGAJIAN: 2004/2005 II

Saya

MUSFA BIN MOHAMAD.
(HURUF BESAR)

mengaku membenarkan laporan projek (PSM/Sarjana/Doktor Falsafah)* ini disimpan di Perpustakaan Universiti Teknologi Malaysia dengan syarat-syarat kegunaan seperti berikut:

1. Laporan Projek Sarjana adalah hakmilik Universiti Teknologi Malaysia.
2. Perpustakaan Universiti Teknologi Malaysia dibenarkan membuat salinan untuk tujuan pengajian sahaja.
3. Perpustakaan dibenarkan membuat salinan laporan projek sarjana ini sebagai bahan pertukaran antara institusi pengajian tinggi.
4. **Sila tandakan (4)

SULIT

(Mengandungi maklumat yang berdarjah keselamatan atau kepentingan Malaysia seperti yang termaktub di dalam AKTA RAHSIA RASMI 1972)

TERHAD

(Mengandungi maklumat TERHAD yang telah ditentukan oleh organisasi /badan di mana penyelidikan dijalankan.

TIDAK TERHAD

(TANDATANGAN PENULIS)

Di sahkan oleh

*(TANDATANGAN PENYELIA)

Alamat Tetap:

PT 11183, KG. SIMPANG
KALLANG 27600
RAUB, PAHANG.PROF. IR. DR. HJ. MOHD WARID HJ. HUSSINTarikh: 4/4/2005Tarikh: 4/4/2005

CATATAN: * Potong yang tidak berkenaan.

** Jika tesis ini SULIT atau TERHAD, sila lampirkan surat daripada pihak berkuasa/organisasi berkenaan dengan menyatakan sekali sebab dan tempoh tesis ini perlu

“ I hereby declare that I have read this project report and in my opinion this project report is sufficient in terms of scope and quality for the award of the degree of Master Engineering (Civil-Structure).

Signature



Name of Supervisor I

PROF. IR. DR. HJ. MOHD WARID HJ HUSSIN

Date

4 April 2005

THE USE OF LIMESTONE AGGREGATE IN CONCRETE.

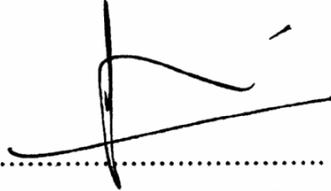
MUSFA BIN MOHAMAD

A project report submitted in partial fulfillment of the
requirements for the award of the degree of
Master of Engineering (Civil Structure)

Faculty of Civil Engineering
Universiti Teknologi Malaysia

APRIL, 2005

I declare that this project report entitled “The use of limestone aggregate in concrete” is the result of my own research except as cited in the references. The project report has not been accepted for any degree and is not concurrently submitted in candidature of any other degree.

Signature : 
Name : MUSFA BIN MOHAMAD
Date : 04 APRIL 2005.

Alfatihah to the passed of my beloved mother and father.
To my beloved Tuan Guru, my wife and my daughters.

ACKNOWLEDGEMENT

In preparing this thesis, I was in contact with many people, researchers, academicians, and practitioners. They have contributed towards my understanding and thoughts. In particular, I wish to express my sincere appreciation to my main thesis supervisor, Professor Ir. Dr. Hj. Mohd. Warid bin Hussin, for encouragement, guidance, critics and friendship. I am also very thankful to Dr. Othman Cik Puan, Dr. Aziz Chik, En. Ros Ismail, En. Suhaimi Abdul Rahman and Technicians from Highway laboratory UTM Skudai for their guidance, advices and motivation in doing all the relevant tests. Without their continued support and interest, this project report would not have been the same as presented here.

I am also indebted to University Teknologi Malaysia (UTM) for finding my Master study. Librarians at UTM also deserve special thanks for their assistance in supplying the relevant literatures.

I am also very thankful to my head of department Majlis Daerah Raub(MDR) Tuan Haji Abdul Rashid Mohamed in preparing this project report, for his advices and also continued support was very much appreciated.

My sincere appreciation also extends to my friends En. Arifin bin Siran (Laboratory Assistance Sekolah Menengah Sulaiman Bentong), Ir. Kamaruddin Hassan (JKR Bridge Section, Kuala Lumpur), Ir. Abdul Kadir Bin Ahyat (Consultant), Ir. Che Husni Ahmad (Consultant), Ir. Azli Shah Bin Ali Bashah

(Engineer of Dewan Bandar Raya Kuala Lumpur) and my colleagues who have provided assistance at various occasions. Thanking to all of you in advanced. I am also very thankful to En. Adnan (Supervisor of Poh Mix. Sdn. Bhd), En. Ramli Abu Bakar (Senior Technician MDR), En. Khairul Effendi Tuaman(Technician MDR) and others who have provided assistance in preparing and making the cubes tests. Very much thankful is also extends to Engineer Mohd Zaid Bin Abdul Samad (From Petronas) who have provided continued support and assistance in preparing the project report.

Lastly, I am also deserve special thanks to my beloved wife for her commitment, encouragement while preparing the works and continued support at various occasions.

ABSTRACT.

Concrete structure is made up of cement, aggregate and water. In building construction the aggregates commonly used are limestone and granite. Three quarters of concrete is made up from aggregate, thus the selection of aggregate should be in the prime condition. To produce a good, strength and high quality concrete the materials used should be in accordance to standard specification. JKR standard specification for building works mentioned that the use of limestone is limited to super structure only whereas for substructure granite aggregate should be used. Due to this problem statement this study is carried out to investigate whether chemical attack in limestone aggregate is the source of problem for sub structure (concrete structure below ground level). This study involved in testing of limestone and granite aggregates. The scope of study includes the investigation on the strength, bonding and chemical attack in the concrete. The main objective of the research is to study the properties of limestone related to strength and its performances. The method of study to be carried out is through the appropriate test. The types of testing required are sieve analysis, flaky and elongation index test, cube test and aggregate crushing value test. All the tests have been carried out and the results had been recorded in appropriate table and graph. Discussion on the analysis of the results is explained to provide more information about the effect of chemical and the behavior of concrete properties. Lastly the conclusion had been done and one recommendation had been introduced for future work.

ABSTRAK.

Struktur konkrit terdiri daripada simen, batu baur dan air. Di dalam pembinaan bangunan, batu baur yang biasa di gunakan ialah terdiri daripada batu kapur dan granit. Tiga suku daripada kandungan konkrit ada lah terdiri daripada batu baur, oleh yang demikian pemilihan batu baur amat lah penting sekali. Untuk menghasilkan konkrit yang baik, kuat dan berkualiti tinggi, maka penggunaan bahan-bahan hendaklah memenuhi spesifikasi piawai. Di dalam spesifikasi Piawai JKR menyatakan bahawa penggunaan batu kapur di hadkan hanya untuk struktur dari tanah keatas sahaja, manakala bagi struktur di bawah tanah hendaklah menggunakan granit. Berdasarkan kepada petikan ini, maka satu kajian untuk menyiasat samaada serangan dari tindak balas kimia merupakan masalah bagi binaan struktur di bawah aras tanah. Kajian ini melibatkan ujian terhadap batu baur jenis batu kapur dan granit. Bidang kajian termasuklah penyiasatan berhubung dengan kekuatan, ikatan dan tindak balas kimia di dalam konkrit. Objektif utama kajian ini adalah untuk mengkaji ciri-ciri batu baur yang berkaitan dengan kekuatan dan keupayaannya. Kaedah kajian ini adalah melalui beberapa ujian yang sesuai. Jenis-jenis ujian tersebut ialah analisis ayakan, indek leper dan indek pemanjangan, ujian kiub dan nilai hancur batu baur. Semua ujian ini telah dijalankan dan keputusannya telah direkodkan dalam bentuk jadual dan graf. Perbincangan mengenai analisis daripada keputusan ujian akan memberikan maklumat berhubung dengan kesan tindak balas kimia terhadap perilaku dan sifat konkrit. Akhir sekali di sertakan satu kesimpulan dan juga satu cadangan untuk kajian di masa depan.

TABLE CONTENT

CHAPTER	TITLE	PAGE
	Title Page	i
	Declaration	ii
	Dedication	iii
	Acknowledgement	iv-v
	Abstract	vi
	Abstrak	vii
	Table of Content	viii-xi
	List of Tables	xii-xiv
	List of Figures	xv-xix
	List of Symbols	xx
	List of Appendices	xi
1	INTRODUCTION	
1.1	Introduction	1-3
1.2	Back ground of the research	3-5
1.3	Significance of the research	5
1.4	Objective of the Study	5-7
1.5	Scope of the research	8-12
2	LIETERATURE REVIEW	
2.1	Introduction	13
2.2	General Information of Aggregate	13-14
2.3	Particles Shape and Texture	14-16
2.4	Bond of aggregate	16

2.5	Theory of rocks	16-17
2.5.1	The Nature of rock	17-18
2.5.2	Igneous rock	18-19
2.5.3	Sedimentation rock	20-22
	2.5.3.1 Carbonate rocks	22
	2.5.3.2 Limestone(Biochemical)	22-23
3	RESEARCH METHODOLOGY	
3.1	Introduction	24
3.2	Experimental framework	24-27
3.3	Experimental Detail	27-29
3.3.1	JKR Standard For Aggregate	29
	3.3.1.1 General Aggregate	29
	3.3.1.2 Fine aggregate	30
	3.3.1.3 Coarse aggregate	31
3.3.2	Aggregate grading	31-32
	3.3.2.1 Sampling and testing of aggregate	32
	3.3.2.2 Storage of aggregate	33
3.4	Water	33
3.5	Types of test Recommended	33-34
3.5.1	Sieve Analysis Test	34-35
	3.5.1.1 Sample of aggregate to be tested	35-36
	3.5.1.2 Elongation and Flakiness Index Test	37-39
3.5.2	Concrete Cube Test	39-40
	3.5.2.1 Preparation of concrete cube grade	40-46
3.5.3	Aggregate crushing value test	46-47
	3.5.3.1 Preparation of limestone aggregate for ACV test	47-53

4	RESULTS AND ANALYSIS	
4.1	Introduction	54
4.2	The Results of sieve analysis	54-57
	4.2.1 Analysis of the Sieve Analysis Results	58
	4.2.2 Analysis of Elongation and Flakiness Index Test	58-59
4.3	Results of Concrete Cube Test	59-62
	4.3.1 Analysis from the results	63
	4.3.1.1 Analysis in respect to strength	63-67
4.4	The results of ACV test	67-68
	4.4.1 Test 1 on the 5 January 2005	68
	4.4.2 Test 2 on the 5 January 2005	68-69
	4.4.3 Test 3 on the 6 January 2005	69-70
	4.4.4 Test 4 on the 6 January 2005	70-71
	4.4.5 Test 5 on the 6 January 2005	71-72
	4.4.6 Test 6 on the 6 January 2005	72-73
4.5	Analyzing the results of ACV test	73-74
	4.5.1 Analysis of limestone aggregate for 7 days in solutions Mg SO ₄ + Na NO ₃ and 7 days in water.	74-76
	4.5.2 Analysis of granite aggregate for 28 days in solutions Mg SO ₄ + Na NO ₃ and 28 days in water.	76-77
5	DISCUSSION	
5.1	Introduction	78
5.2	Discussion on the texture of aggregate	78-79
	5.2.1 The source of limestone aggregate	79
	5.2.2 Discussion on the Sieve Analysis	80
5.3	Discussion on Flaky and Elongation Properties	80-81

5.3.1	What can be discussed on the Flaky and Elongation Properties?	80-81
5.4	Discussion about Concrete Cube Strength	81-82
5.4.1	Cube Strength 7 days period	82-84
5.4.2	Cube Strength 14 days period	84
5.4.3	Cube Strength 21 days	84-85
5.4.4	Cube Strength 28 days	85-87
5.5	Discussion on ACV Test results	87
5.5.1	Discussion on ACV test for 7 days	88-92
6	CONCLUSION AND RECOMMENDATION	
6.1	Introduction	93
6.2	Conclusion	94
6.3	Recommendation	94-95
	REFERENCES	96-98
	APPENDICES A – C2	99-103

LIST OF TABLES

TABLE NO.	TITLE	PAGE
1.1	Classification of natural aggregates according to rock type (BS812: Part 1 : 1975)	2
1.2	Coarse Aggregate (Nominal Size 20 mm) - Standard specification Section 2 to 6 M.S. 7.5)	9
1.3	Testing of aggregate	9
1.4	Minimum Strength Specification of Concrete Cube (150x150x150).	10
2.1	Particle Shape Classification of BS 812: Part 1: 1975 with examples.	15
2.2	Compressive Strength of American Rocks Commonly Used as Concrete Aggregates.	17
2.3	Minerals crystallization from magma.	18
2.4	Minerals present in the four main groups of Igneous rock.	19

2.5	Chemistry of selected carbonate rocks sediment.	23
3.1	Date of Cube test.	27
3.2	Fine Aggregate (Natural sand)	32
3.3	Coarse Aggregate (Nominal size 20 mm).	32
3.4	Position of Sieve size	36
3.5	Standard Format for Calculation of Elongation And Flakiness Index Test.	38
3.6	The mix proportion of Concrete Cube Grade 25.	40
3.7	Date of Casting and Testing of Concrete Cube.	44
3.8	Quantity of aggregate/ Mg SO ₄ + Na NO ₃ and water Content.	48
3.9	Date of Immersion and Taken out of an Aggregate.	49
4.1	Results of Sieve Analysis of Limestone Aggregate.	55
4.2	Results of the Elongation and Flakiness Index of Limestone aggregate.	57
4.3	Comparison of Aggregate Passing to JKR specification.	58
4.4	The Results of Cubes Test.	60

4.5	The Results of Cube Strength Compare to JKR Specification.	64
4.6	Comparison of Compressive Strength of Rock to Concrete Cube.	66
4.7	Data Record of ACV Test 1 (14-10 sieve).	68
4.8	Data Record of ACV Test 2 (14-10 sieve).	69
4.9	Data Record of ACV Test 3 (20-14 sieve)	70
4.10	Data Record of ACV Test 4 (20-14).	71
4.11	Data Record of ACV Test 5 (14-10)	72
4.12	Data Record of ACV Test 6 (20-14)	73
5.1	The Results of Acv test for Limestone and Granite.	87
5.2	Results of ACV test for Granite and Limestone (28 days).	91

LIST OF FIGURES.

FIGURE NO	TITLE	PAGE
1.1	Sample of limestone aggregate (Source from Kg. Ulu Gali, Raub, Pahang).	2
1.2	Sample of Aggregate.	8
1.3	Sample of concrete cube with 150x150x150 in size.	11
1.4	Sample of Chemical (Magnesium Sulphate + Natrium Nitrate)	12
2.1	How sedimentation rock is formed.	20
2.2	Limestone Rock (Sample 1)	21
2.3	Limestone Rock (Sample 2)	21
3.1	Preparation of Chemical solution	25
3.2	Immersion of cubes in to chemical solution.	26
3.3(a)	Front view of Gunong Panas, Ulu Gali, Raub.	28

3.3(b)	Side View of Gunong Panas, Kg. Ulu Gali, Raub.	28
3.4	The Sieve Analysis Apparatus.	30
3.5	Sample of Limestone and granite aggregate in UTM Highway Laboratory.	31
3.6	Source of Limestone from Gunong Panas, Kg. Ulu Gali, Raub, Pahang.	34
3.7	Sample of limestone aggregate for Sieve Analysis Test.	35
3.8	Apparatus in Sieve Analysis Test.	36
3.9	Apparatus for Elongation and Flakiness Index Test (Steel Plate With Standard Hole)	37
3.10	Procedure for Elongation and Flakiness index test	39
3.11	Preparation of Concrete Cubes.	41
3.12	Procedure in Preparation of Cube.	41
3.13	Step to prepare 150x150x150 Concrete Cube	42
3.14	Measuring The Slump of Fresh Concrete	43
3.15	Preparing the concrete cubes	43
3.16	Weighting the Cube Sample	44

3.17	Testing of Cube	45
3.18	Recording Compressive Strength From Dial Gauge	45
3.19	Failure Pattern of Cube.	46
3.20	End of The Test	46
3.21	Weighting of Limestone Aggregate for ACV Test	50
3.22	Placing Aggregate in to the Mould	51
3.23	Aggregate under Testing (400kN/10 minutes)	51
3.24	Aggregate Under Rate of Crushing	52
3.25	Sample of Aggregate after Crushing	52
3.26	Crushed Sample of Aggregate Retain on 2.36 Sieve	53
4.1	Graph of Sieve Analysis Test for Limestone Aggregate	56
4.2	Relationship Between Elongation/Flakiness Index and JKR Standard.	57
4.3	Limestone Concrete Cube Strength in Chemical Solution for 7 days.	61
4.4	Limestone Concrete Cube Strength in Water for 7 days.	61

4.5	Limestone Concrete Cube Strength in Chemical Solution for 28 days.	62
4.6	Limestone Concrete Cube Strength in Water for 28 days.	62
4.7	Limestone Concrete Cube Strength Compared to JKR Standard for 7 days (Average Strength)	64
4.8	Limestone Concrete Cube Strength Compared to JKR Standard for 28 days (Average Strength).	65
4.9	Relationship Between Concrete Cube Compressive Strength To Original Rock.	67
4.10	Results of Aggregate Crushing Value Test for 7 days in Chemical Solution and Water.	74
4.11	Results of Limestone Aggregate Crushing Value Test for 28 days in Chemical Solution and Water.	75
4.12	Results of Aggregate Crushing Value of Granite for 28 days.	76
5.1	Types of Aggregate Texture	81
5.2(a)	Failure Pattern in Water	83
5.2(b)	Failure Pattern in Chemical Solution	84
5.3(a)	Average Cube Strength of Limestone Concrete in Chemical Solution.	84

5.3(b)	Average Cube Strength of Limestone Concrete in Water.	84
5.4(a)	Results of Limestone ACV Test for 28 days in Chemical Solution and Water.	89
5.4(b)	Results of Granite ACV Test for 28 days in Chemical Solution and Water.	90
5.4(c)	Results of ACV Test for Granite and Limestone Aggregate in Chemical Solution (28 days)	91
5.4(d)	Results of Granite and Limestone Aggregate on ACV Test for 28 days in Water.	92

LIST OF SYMBOLS

B.S	-	British Standard
>	-	More than
<	-	Less than
G25	-	Grade 25
Mg SO ₄	-	Magnesium Sulphate
Na NO ₃	-	Natrium Nitrate
Ca O	-	Calcium Oxide
Mg O	-	Magnesium Oxide
CO ₂	-	Carbon Dioxide
S1,S2,ect	-	Sample in Chemical Solution
S.O	-	Superintendent Officer
ACV	-	Aggregate Crushing Value
JKR	-	Jabatan Kerja Raya
Fe O	-	Ferrous Oxide
Mn O ₂	-	Manganese Dioxide
Ca(OH)	-	Calcium Hydroxide
Mpa	-	Mega Pascal
Psi	-	Ib/square in.
Ca CO ₃	-	Calcium Carbonate (Limestone)

LIST OF APPENDICES

APPENDIX	TITLE	PAGE
A1	JKR Specification page 35	99
A2	JKR Specification page 36	100
B	JKR Standard Limit for Laboratory Testing	101
C1	Cube Test Results 7 days in Water	102
C2	Cube Test Results 7 days in Chemical Solution	103

CHAPTER 1

INTRODUCTION

1.1 Introduction.

Since concrete is the most important part in structural construction, the aggregate content should be in a form of good strength for structural purposes. Concrete is made up of aggregate, cement and water. Through this combination of materials, three – quarter of the mix is governed by aggregate. The aggregate itself is categorized as fine and course aggregate.

In this study, the scope of research will be focused on the use of coarse aggregate using lime stone material. Before further discussion, it shall be better to have knowledge and clear understanding about the lime stone material and its properties and performances.

Lime stone is one of the aggregate to be used in concrete, other than that are granite, basalt, Quardz, Gneis, Gabbro, Sand stone, Felsit ect. The classification of the aggregates according to BS 812 :Part 1 :1975 as stated from table 1.1 in this chapter.



Figure 1.1 : Sample of Limestone Aggregate (Source from Kg. Ulu Gali, Raub, Pahang)

Table 1.1: Classification of natural aggregates according to rock type (BS 812 : Part 1 :1975)

Basalt Group	Flint Group	Gabbro group
Andesite Basalt Basic porphyrites Diabase Dolerites of all kinds including theralite and teschenite. Epidiorite Lamprophyre Quartz-dolerite Spilite	Chert Flint	Basic diorite Basic Gneiss Gabbro Hornblende-rock Norite Peridotite Picrite Serpentinite
<u>Granite Group</u>	<u>Gritstone Group</u>	<u>Hornfels group</u>

Gneiss	<u>(including fragmental volcanic rocks)</u>	Contact-altered rocks of all kinds except marble.
Granite		
Granodiorite	Arkose	
Granulite	Greywacke	
Pegmatite	Grit	
Quartz-diorite	Sandstone	
Syenite	Tuff	
<u>Limestone Group</u>	<u>Porphyry Group</u>	<u>Quartzite Group</u>
Dolomite	Aplite	Ganister
Limestone	Dacite	Quartzitic sandstones
Marble	Felsite	Re-crystallized quartzite.
Schist Group	Granophyre	
	Keratophyre	
	Microgranite	
Phyllite	Porphyry	
Schist	Quartz-porphyrite	
Slate	Rhyolite	
All severely sheared rocks.	Trachyte	

Page 110: Properties of Concrete – A.M. Neville

1.2 Back ground of the research

Limestone and granite are two types of aggregates commonly used in industrial construction. For JKR project, the used of limestone aggregate is limited to

super structure only whereas for substructure there is no recommended to use limestone below ground level. Due to this statement the study is to be carried out to find what source of the problems in related to concrete below ground level. One of the problems in the ground level is about chemical attack, so that a few numbers of laboratory test should be carried out to get the results for analysis purposes.

In conjunction to this matter, the problem arises is based on the JKR specification mention under Section D (Concrete Work) item 3.0 for aggregate contents.

From Item 3.3 Coarse Aggregates:

Standard Specifications For Building works page 35 standard specification for building works written as below:-

“The coarse aggregate shall be crushed hard stone except that for work below ground level, only crushed granite will be used. The aggregate shall not contain clay lumps exceeding 1% by weight. A representative dry sample shall not show an increase in weight exceeding 8% after immersion in water when tested according to the method in M.S. 7.5. It shall be well shaped and not flaky with the flakiness index not exceeding 35%. The maximum nominal size of coarse aggregate shall be 19mm.”

Through the statement above, it is understood that the use of limestone aggregate was not recommended in building works below ground level. Since concrete work is the importance structure, understanding about the material properties shall be significantly in the advanced condition. A few tests to get the strength should be carried out in the laboratory and the results can be analyzed. The results obtained can be compared to the standard specification for building's work. So, through this study I would like to further the use of limestone in a certain area as alternative to granite aggregate.

The main reason to study this topic is to get better knowledge and to bare in mind **whether “ Chemical Attack below ground level “** source of the problem in using limestone concrete structure. In the preparation of this thesis, many factors should be considered and there must be some references towards the study for getting clear information and understanding about the chemical attack in concrete structure. At the end of this study, a conclusion can be made according to the results obtained through the laboratory tests.

1.3 Significance of the research.

In construction industries, the use of aggregates is the most importance material in composition of concrete. Places having granite aggregate should have no problem in construction projects, but for places without granite the problems will be arises and cost incurred become higher. Due to this reason this study should be carried out in the approaching method to overcome the problem as well as beneficial to local people.

The advantages of this study are:-

- i) To provide some information about the used of limestone aggregate.
- ii) Beneficial and economic value to local people.
- iii) New finding during the test and methods required to overcome the problems.
- iv) Have chances to explore the used of local material in construction industries.

1.4 Objective of the study.

In our country, stone can be selected from a certain area which is in the form of various types of materials such as granite, limestone, basalt, quartz, gneiss, gabbro, sand stone and others as stated in table 1.0 from the previous paragraph.

Area of easily granite formed shall have no problems for concrete structure, but for an area of without granite and limestone easily selected this might be incurred cost to import granite aggregate from other places. As a result, this also will reduce the beneficial economic value for that particular place due to granite demand.

The main issue of this study is to identify whether the chemical reaction can affect the concrete structure from limestone aggregate below ground level. In the ground, there are various types of chemical reactions such as sulfate, chloride, nitrate, sodium, atrium and others soluble exist in that particular places. For this purpose, every places will have different soluble in the ground and its depend on the types of soil or rock for that particular area.

At the end of this study some information regarding limestone aggregate will be obtained from the test results. Due to the results required, the beneficial values of the study can be shared together and its will bring objectives as the followings:-

i) To study the limestone properties related to strength and its performances.

In this objective, the strength of the limestone should be obtained in many ways. One of the methods is cube test. However the method pertaining to this matter will be discussed on the next topic under chapter 2 under methodology section.

Through this objective, all the information should be collected and might be one of the proven sign to get a solution to the problem. If there is exist, it means that the limestone aggregate is no longer to be a selected and approved material in concrete structure. For this purpose, the specification of JKR should the one to refer and compared with the results of the tests.

ii) To compare the results with granite concrete and costing required.

As according to JKR specification in building works, the use of granite is the recommended aggregate in construction of JKR projects. For this particular situation, the comparison between limestone and granite is the options to get some information to public use and acknowledgement purposes.

Since granite concrete is no matter stronger and its characteristic strength is more than limestone concrete, so that the results of the cube tests is significantly functioning to this study. Because of the local interest to economic value, the cost incurred for both types of aggregate will be established to public information.

iii) To provide the information on demands of local material and its benefits.

Once the result of the tests is recorded, there are specifics analysis can be ascertained and very important factors to encourage people on the demands of each materials. For this particular objective, the demand on limestone is predictably on advanced because the study is focusing to the local materials on the beneficial aspects especially on the economic aim.

However, in promoting the local material demands there must be a specific reason and advantages to welcome people without prejudice. Through this study, it will provide some guide lines and references for really problems arise towards the specific solution otherwise there are no neglected inspiration exists. Once it's come through there are clear information to people involved in construction industries.

iv) As an alternative materials without prejudice.

If the concrete made of limestone aggregate can produce a strength and durability, therefore its performance is good for concrete structure. The important

thing in construction technology is the material used is followed the specification and the test results should according to specification. Any materials set the specification, meaning that the material can be used for construction purposes. In the case of limestone, it also a type of aggregate involved in obtaining a good concrete provided the required test should followed the specification in the contract document.

1.5 Scope of the research.

The construction industries are becoming more challenging than ever before. To be competitive, the field of engineering related to the industries has to be established. One of the areas that can be established is the used of material in the construction purposes. A specific scope of study on the limestone aggregate is presented in this paper as to improve the knowledge in the field of construction technology.

1.5.1 Bond of aggregate :

The bond between aggregate and cement paste is essential to produce the flexural strength of concrete, but the nature of this bond is not fully understood. For this reason, an analysis needs to be conducted by performing specific tests in the laboratory. The flakiness index and elongation tests on the limestone aggregate are required that to prove the specification in JKR contract document is met. Bonding between aggregate and cement paste depends on the surface of the aggregate. Since the rough surface requires more bonding than the smooth surface, the texture of aggregate to be tested should comply to the requirement of standard specification.



Figure 1.2: Sample of aggregates (left is limestone, right is granite).

The aggregate used in the tests must comply to the standard grading which is through sieve analysis test with 4 kilogram of limestone aggregate sample. The test shall follow a proper procedure and the results are compared to the standard as tabulated in Table 1.2 below:-

**Table 1.2: Coarse Aggregate (Nominal Size 20 mm) – Standard specification
Section 2 to 6 M.S. 7.5**

British Standard Sieve	20 mm	10 mm	5 mm
Percent passing (%)	100	25-55	0-10

The flakiness and elongation tests shall comply to the standard specification listed in Table 1.3 below:-

Table 1.3: Testing of aggregate (Refer Appendix B).

Properties	Types of aggregate	Test Methods	Limits
Grading Elongation Index Flakiness Index Aggregate Crushing Value	Coarse Coarse Coarse Coarse	M.S 7.5 M.S 30 M.S 30 M.S 30	As mention in Table 2.1 Not exceeding 30% Not exceeding 35% Not exceeding 40%